

Use of Monosaccharides in Metal-Catalyzed Coupling Reactions

Sara H. Kyne^{*,†} and Jason E. Camp^{*,‡}

[†]School of Chemistry, University of Lincoln, Lincoln LN6 7TS, United Kingdom

[‡]Department of Chemical Sciences, University of Huddersfield, Huddersfield HD1 3DH, United Kingdom

ABSTRACT: The addition of monosaccharides to metal-catalyzed coupling reactions can be beneficial in terms of decreasing the time required, chemical waste products and overall cost of the process. Monosaccharides are used in a number of different ways, including (a) acting as a ligand for the metal, (b) providing the appropriate reduction potential for a chemical process and (c) acting as a reducing agent for the formation and stabilization of catalytically active metal nanoparticles. Recently, there has been a significant amount of research in this growing field and there is thus the potential for the addition of monosaccharides to coupling reactions to have a significant impact on the synthesis of the important small molecules on which we have all come to rely. This Perspectives Article will cover recent developments in the addition of monosaccharides to metal-catalyzed coupling reactions with an emphasis on their utility and limitations in order to facilitate the further development of this exciting area of research.

KEYWORDS: Monosaccharide, Biorenewables, Metal catalysis, Green chemistry, Nanoparticle




INTRODUCTION

Metal-catalyzed coupling processes are a ubiquitous part of the modern chemists' toolkit for the synthesis of added-value small molecules on which we have all come to rely. To make these processes more efficient, in terms of time, expense and cost to the environment, unmodified monosaccharides have been added to metal-catalyzed reactions as part of research into the use of biorenewables in catalytic/chemical reactions. The addition of monosaccharides can serve many purposes in these reactions, including (a) acting as a ligand for the metal, (b) providing the reduction potential for a chemical process and (c) acting as a reducing agent for the formation and stabilization of catalytically active metal nanoparticles. The ability of monosaccharides to reduce metals has been known for decades,¹ for example Benedict's² or Fehling's tests,³ but their use in cross-coupling reactions has flourished in recent years. This review will focus on the latest uses of monosaccharides in metal-catalyzed coupling reactions. Because of recent reviews and full publications, the following areas will not be covered in this review: polysaccharides,^{4–9} smaller sugar derived aldehydes/carboxylic acids (Leuckart–Wallach reaction)^{10–16} or reactions in which sugars are used as starting materials or incorporated into the molecule.^{17–24}

MONOSACCHARIDES AS LIGANDS

One of the most common uses of monosaccharides in metal-catalyzed reactions are as ligands for a catalytically active metal species.²⁵ For example, Sekar and Thakur recently disclosed the synthesis of phenols **2** from aryl halides **1** in a process that was catalyzed by a copper/glucose system (Scheme 1).²⁶ Aryl iodides and bromides **1** were reacted with excess potassium

Scheme 1. Synthesis of Phenols **2** from Aryl Halides **1**

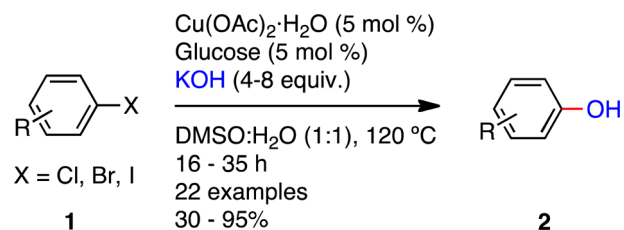


hydroxide (4–8 equiv) in the presence of copper(II) acetate (5 mol %) and D-glucose (5 mol %) to give good to excellent yields of the corresponding phenols **2**. The reactivity of aryl chlorides depended on the nature of the electron withdrawing group with substrates containing a nitro group giving an excellent yield of phenol **2**.

Recently, a number of carbon–nitrogen cross-coupling reactions have been developed employing a catalytic system formed *in situ* from copper(I) iodide and D-glucosamine in the presence of base.²⁷ For example, anilines were formed from aryl halides in the presence of excess aqueous ammonia (10 equiv) or sodium azide (3 equiv).^{28,29} Zhang et al. reported the use of similar conditions for the cross-coupling of aryl halides **3** with nitrogen heterocycles **4** (1.2 equiv.; Scheme 2).³⁰ Most of the examples used imidazole as the heterocycle **4**, and good yields were observed for aryl iodides **3** bearing electron-withdrawing

Received: August 10, 2016

Revised: September 12, 2016


Scheme 2. Cross-Coupling of Aryl Halides 3 with Nitrogen Heterocycles 4

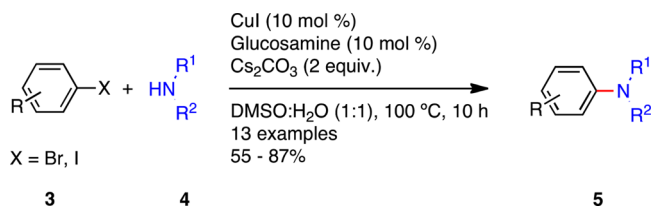

groups. Unfortunately, the reaction did not occur with aryl chlorides.

Zhang et al. extended this methodology to carbon–sulfur cross-coupling reactions. In this work, aryl iodides 6 were reacted with diphenyl disulfide (7, 0.6 equiv) in the presence of copper(I) iodide (10 mol %), D-glucosamine (10 mol %) and cesium carbonate (2 equiv) to give the corresponding unsymmetrical diaryl sulfide 8 (Scheme 3).³⁰ When aryl


Scheme 3. Carbon–Sulfur Cross-Coupling Reaction

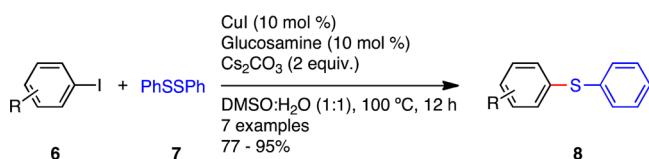

bromides were tested the reaction occurred, but required 24 h to go to completion. Similar methodology was used by the same group to synthesize a variety of diaryl sulfones from aryl halides and sodium benzenesulfonates.³¹

D-Glucosamine has also been successfully employed as a ligand in iron-catalyzed Grignard cross-coupling reactions of vinylic 10 and allylic bromides 11 (Scheme 4). Phenyl- or


Scheme 4. D-Glucosamine Successfully Employed as a Ligand in Iron-Catalyzed Grignard Cross-Coupling Reactions

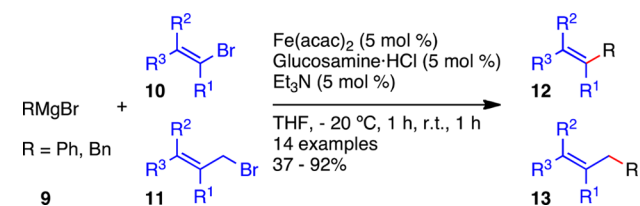

benzylmagnesium bromides 9 were reacted with bromides 10 or 11 in the presence of iron(II) acetylacetonate (5 mol %) and D-glucosamine hydrochloride (5 mol %). Triethylamine (5 mol %) was added to deprotonate the ligand and thus increase its solubility in THF.³² Moderate yields of substituted alkenes 12 were obtained from allylic bromides 10, and good yields of the sp^3 -hybridized products 13 were obtained from alkenyl bromides 11.

D-Glucosamine was shown to improve the yield in palladium-catalyzed Mizoroki–Heck reactions of aryl halides (Scheme 5).³³ Aryl halides 14 were reacted with activated alkenes 15 (1.2 equiv) in the presence of palladium(II) acetate (0.5 mol %), D-glucosamine (1 mol %) and potassium carbonate (2.0 equiv). Aryl iodides and bromides afforded good to excellent conversion to stilbenes 16 with unsubstituted and *para*-substituted electron withdrawing groups. Conversion was

Scheme 5. D-Glucosamine Shown To Improve Yield in Palladium-Catalyzed Mizoroki–Heck Reactions of Aryl Halides

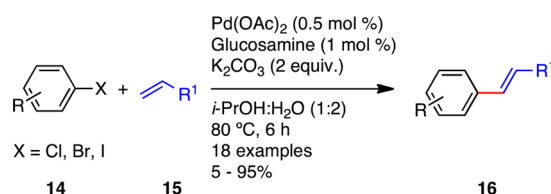


moderate when the arene was substituted at the *ortho* position. Aryl chlorides 14 reacted, albeit with low conversion (5–25%).

MONOSACCHARIDES FOR NANOPARTICLE FORMATION

One of the most common uses of monosaccharides in organic transformations are as reductants for the formation of metal nanoparticles, in which the sugar serves to reduce the metal in the presence of a template.^{34–45} Monosaccharides, glucose in particular, have also been used as supports for metal nanoparticles.^{46–49} In some cases, the monosaccharides act as both the stabilizer for the metal nanoparticles as well as the reducing agent.^{50–54} Alternatively, additional reducing agents can be added to the mixture of sugar and metal if required. For example, monodispersed colloidal carbon spheres have been synthesized by a two-step hydrothermal approach under mild conditions by Sun et al.⁵⁵ In this work, separating the nucleation and growth steps allowed for a narrow size distribution with diameters ranging from 160 to 400 nm. Interestingly, the size distribution decreased with an increasing concentration of glucose. D-Glucose has also been used as the metal nanoparticle support. In this case, palladium(0) nanoparticles were synthesized by the reduction of $\text{H}_2[\text{PdCl}_4]$ or $[\text{Pd}(\text{NH}_3)_4\text{Cl}_2]\text{Cl}_2$ in the presence of excess hydroxylamine and D-glucose under ambient, aqueous conditions.⁵⁶ Characterization of the palladium nanoparticles revealed magnetization differences depending on the oxidation state of the palladium precursor. TEM analysis revealed that when starting from the Pd(II) complex, the nanoparticles were an average size of 6 nm and polydispersed, whereas starting from the Pd(IV) complex formed nanoparticles with an average size of 8 nm that were mainly monodispersed. In 2004, Sun and Li reported the synthesis of colloidal carbon spheres starting from glucose, which underwent subsequent functionalization due to the reactive surface present.⁵⁷ For example, the FTIR spectrum revealed the existence of carbonyl and hydroxyl groups that maintained the hydrophilicity of the carbon spheres. Colloidal carbon spheres were prepared from aqueous glucose by hydrothermal synthesis, undergoing aromatization and carbonization to form 200 nm carbon spheres at 160 °C in 3.5 h, and 1500 nm at 180 °C in 10 h. Under reflux, palladium(0) nanoparticles were loaded onto the surface, covering the carbon spheres with a uniform shell of 10–20 nm palladium. In related methodology, Zhang et al. described the preparation of highly dispersed, narrow diameter palladium nanoparticles on carbon spheres via *in situ* reduction.⁵⁸ Precise control of the dispersity and size of the palladium(0) nanoparticles was possible by careful adjustment of the reaction conditions (temperature, time, pH and ratio of palladium(0) to carbon spheres). Homogeneously distributed, small diameter (7.7 nm) palladium crystals were prepared on carbon spheres at pH 7.0 in ethanol at 70 °C.

The isolated metal nanoparticles have subsequently been used in a number of important catalytic processes. For example, Sen et al. recently reported a palladium(0) nanoparticle catalyzed domino Sonogashira-cyclization reaction to synthesize various isoindolinones **20** and furoquinolines **21** in good yields (Scheme 6).⁵⁹ Palladium(0) nanoparticles were prepared

Scheme 6. Palladium(0) Nanoparticle Catalyzed Domino Sonogashira-Cyclization Reaction to Synthesize Various Isoindolinones **20 and Furoquinolines **21****

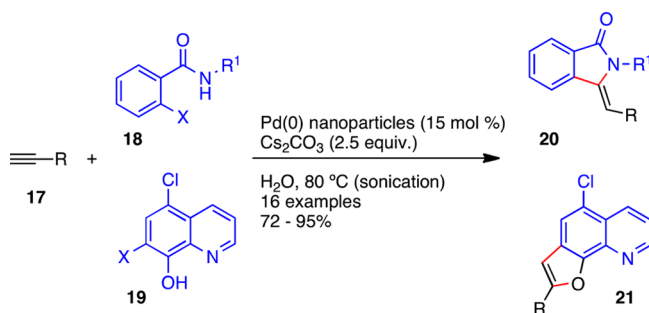


by the procedure of Sarkar et al. in which $\text{H}_2[\text{PdCl}_4]$ was reduced in the presence of hydroxylamine and D-glucose under aqueous conditions.⁵⁶ Following the reaction, the catalyst could be recovered in high yield and a recycling study showed only a gradual decrease in activity for up to five subsequent reactions before significant loss of yield was observed.

MONOSACCHARIDES AS REDUCTANTS IN CHEMICAL PROCESSES

Monosaccharides can also be added to organic transformations to act as reductants for chemical process that occur in the absence of catalyst^{60,61} or to reduce a metal precatalyst to the necessary oxidation state *in situ* so that the reaction can proceed. This concept has been employed for a variety of reactions such as dehalogenations,⁶² reductions^{63–66} and coupling processes. Glucose can also be used for the *in situ* formation of the active metal catalyst. For example, Cuevas-Yañez et al. showed that addition of 25 mol % of glucose to the reaction mixture resulted in an increased yield of the desired triazoles **24** from alkynes **22** and azides **23** under copper-catalyzed click reaction conditions (Scheme 7).⁶⁷

Scheme 7. Increased Yield of the Desired Triazoles **24 from Alkynes **22** and Azides **23** under Copper-Catalyzed Click Reaction Conditions**

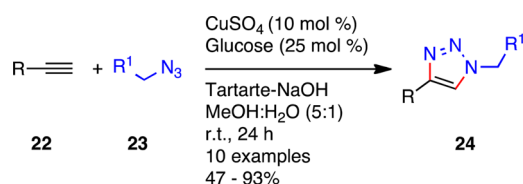

In related work, Singh et al. showed that it was beneficial to add glucose to copper-catalyzed click reactions⁶⁸ that were part of multicomponent coupling reactions under microwave conditions (Scheme 8). Thus, the three component reaction of phenylazides **25**, 4-(prop-2-yn-1-yloxy)benzaldehydes **26**, and 1,2-diaminobenzenes **27** afforded the triazole adducts **28** in good yields (Scheme 8a).⁶⁹ Additionally, a four component process resulted in the efficient formation of 3-phenyl-2-[4-((1-

phenyl-1H-1,2,3-triazol-4-yl)methoxy}phenyl]thiazolidin-4-ones **29** from readily available starting materials (Scheme 8b).⁷⁰ In both cases, the glucose is purported to reduce the copper to the catalytically active species. Related work by Wan et al. demonstrated that copper–glucose systems catalyzed the three component reactions of phenols, acyl chlorides and Wittig reagents to form β -aryloxy acrylates.⁷¹ Furthermore, Guchhait et al. developed a novel A³-coupling methods for the synthesis of N-fused imidazoles using a copper(II) sulfate–glucose catalyst.⁷² This methodology was subsequently harnessed by Iyer et al. for the synthesis of luminescent imidazo[1,2-a]pyridines.⁷³


MONOSACCHARIDES FOR THE *IN SITU* FORMATION/STABILIZATION OF CATALYSTS

One of the most important advances in this area is the ability to form catalytically active metal nanoparticles *in situ* from unmodified reducing sugars and subsequently recycle the catalyst. Traditionally, bioderived metal catalysts need to be synthesized and isolated prior to reaction, and are frequently difficult to recycle following the reaction, which can increase the amount of time, chemical waste and expense of the overall process.^{74–81} Building upon the work in nanoparticle formation from reducing sugars, and the use of reducing sugars as reductants in catalytic processes, Nacci et al. recently disclosed an Ullman type homocoupling of aryl halides catalyzed by *in situ* generated palladium(0) nanoparticles (Scheme 9).⁸² Thus, the homocoupling of bromo- and chloroarenes **30** in the presence of glucose (0.5 equiv), palladium(II) acetate (3 mol %) and tetrabutylammonium hydroxide (3.0 equiv) afforded the desired biaryls **31** in good yield. In this process, the glucose is postulated to both reduce the palladium(II) acetate to the catalytically active palladium(0) species, as well as stabilize the *in situ* formed catalyst through the formation of nanoparticles. In contrast to other related reports (*vide infra*), exogenous capping agents were used in this study. TEM analysis was used to confirm the formation of nanoparticles, which had an average particle size around 15 nm, and XPS was used to show that the palladium in the isolated nanoparticles was in the zero oxidation state. A recycling study demonstrated that the catalytic solution was active for 3 cycles, but the yield decreased precipitously thereafter.


Nacci et al. also showed that an Ullman type homocoupling of haloarenes **32** to give the corresponding biaryls **33** could be facilitated by gold nanoparticles formed *in situ* from the reduction of gold(III) acetate (2 mol %) with a stoichiometric amount of glucose (Scheme 10).⁸³ This catalytic system was active for bromo- and iodo-substituted arenes **32**, as well as alkenes. The less reactive aryl chlorides were found to be unreactive under the reaction conditions. It was also found that the ionic liquid tetrabutylammonium acetate (TBAA) was a competent solvent and base for the reaction, which could substitute for water. Interestingly, the nanoparticles formed in the ionic liquid were much larger than those formed in water (ca. 2 nm vs. Twenty nm respectively) and in general resulted in a decreased yield compared to the aqueous conditions. Unfortunately, attempts at recycling these catalysts showed a similar poor performance to the palladium system discussed above (cf. Scheme 9).

Recently, we disclosed methods for the use of glucose derived palladium(0) nanoparticles as *in situ* formed catalysts for Suzuki–Miyaura cross-coupling reactions in the green solvent isopropyl alcohol (Scheme 11).⁸⁴ The cross-coupling of


Scheme 8. Four Component Process Resulted in the Efficient Formation of 3-Phenyl-2-[4-((1-phenyl-1*H*-1,2,3-triazol-4-yl)methoxy)phenyl]thiazolidin-4-ones 29

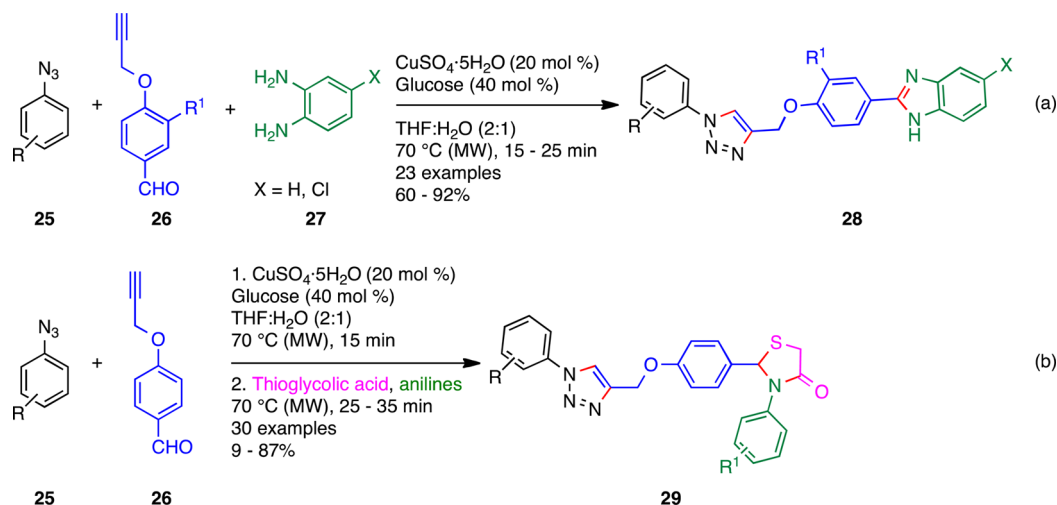


Scheme 9. Ullman Type Homocoupling of Aryl Halides Catalyzed by *in Situ* Generated Palladium(0) Nanoparticles

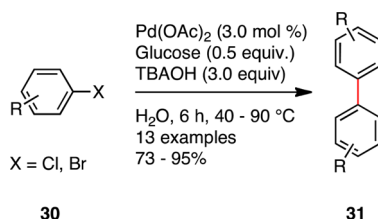

Scheme 10. Ullman Type Homocoupling of Haloarenes 32 To Give Corresponding Biaryls 33 Facilitated by Gold Nanoparticles Formed *in Situ* from Reduction of Gold(III) Acetate with Stoichiometric Amount of Glucose

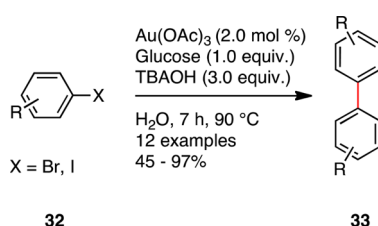


Scheme 11. Use of Glucose Derived Palladium(0) Nanoparticles as *in Situ* Formed Catalysts for Suzuki–Miyaura Cross-Coupling Reactions Green Solvent Isopropyl Alcohol

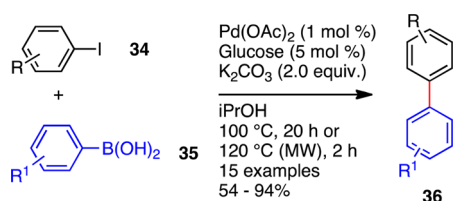

analysis of the *in situ* formed nanoparticles showed that the 251
palladium was surrounded by a hydrophilic, hydroxylated shell. 252
The hydrophilic/polar nature of the nanoparticles allowed for 253
their facile removal from the cross-coupled product. ICP-MS 254
analysis showed a 65% decrease in the amount of metal 255
incorporated into the final compounds compared to reactions 256
that did not contain glucose. Interestingly, Jiang and Fossey et 257
al. have found that monosaccharides bind to boronic acid to 258
form the less reactive boronate ester. They used the retardation 259
of the Suzuki–Miyaura homocoupling reaction to develop 260
fluorescent sensors for glucose detection. 261

Subsequently, Jain et al. described the use of reducing sugars 262
in palladium mediated cross-coupling reactions, in which the 263
metal was catalyzing multiple, mechanistically distinct steps; 264
autotandem catalysis^{87,88} (Scheme 12).⁸⁹ After screening nine 265 s12

Scheme 12. Use of Reducing Sugars in Palladium Mediated Cross-Coupling Reactions

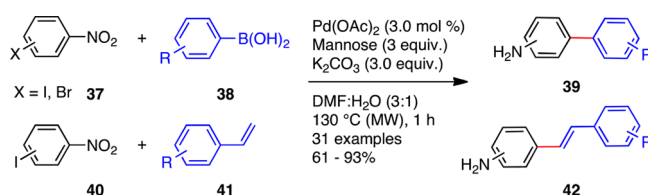


difference reducing sugars, they found that the addition of 266
mannose (3 equiv) gave the desired cross-coupled products of 267
Suzuki–Miyaura and Mizoroki–Heck reactions, while con- 268
currently reducing the nitro functionality to an aniline. For 269
example, reaction of halo-nitrobenzenes 37 with arylboronic 270
acids 38 in aqueous DMF at 130 °C (microwave) gave the 271
coupled biaryl anilines 39 in moderate to excellent yields. 272
Similarly, the reaction of iodo-nitrobenzenes 40 with styrenes 273
41 under the same reaction conditions afforded substituted 274
amino-stilbenes 42 in good to excellent yields. It is unclear from 275
the analysis conducted by the researchers whether the mannose 276
is simply acting as a ligand and source of hydrogen under the 277
reaction conditions, or if it is also stabilizing *in situ* formed 278
nanoparticles. 279

Building upon our work discussed above, we recently 280
reported the use of glucose derived nanoparticles for the 281

245 aryl iodides 34 and aryl boronic acids 35 in the presence of
246 palladium(II) acetate (1 mol %) and glucose (5 mol %) gave
247 the desired biaryls 36 in moderate to good yields under either
248 thermal or microwave heating conditions. In contrast to the
249 reports of Nacci et al., only a small amount of glucose was
250 required and no capping agents were employed. EF-TEM

282 Mizoroki–Heck, Sonogashira and Suzuki–Miyaura cross-
283 coupling reactions in aqueous solvents (Scheme 13).⁹⁰ The

Scheme 13. Use of Glucose Derived Nanoparticles for the Mizoroki–Heck, Sonogashira and Suzuki–Miyaura Cross-Coupling Reactions in Aqueous Solvents

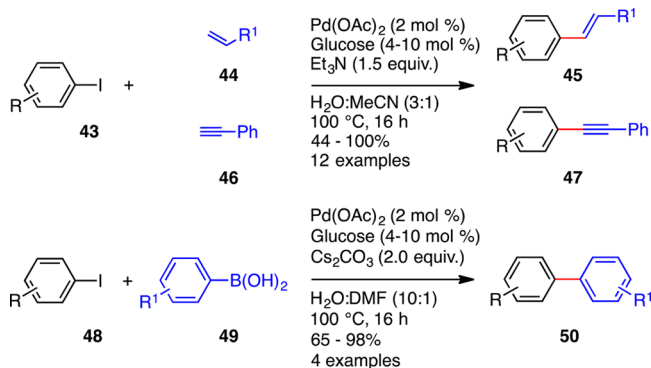

284 reaction of aryl halides **43** with alkenes **44** or alkynes **46**
285 proceeded in moderate to excellent yields to afford stilbenes **45**
286 or substituted alkynes **47**, respectively. The palladium(0)
287 nanoparticle catalysts were formed *in situ* from palladium(II)
288 acetate (2 mol %) via the addition of glucose (4–10 mol %) to
289 the reaction. In addition, a Suzuki–Miyaura protocol for the
290 synthesis of biaryls **50** in aqueous DMF was developed using
291 the same *in situ* derived palladium(0) nanoparticles. Import-
292 tantly, this protocol was also viable for aryl bromides. In
293 contrast to the study by Jian et al.,⁷⁴ the nitro functionality was
294 not reduced in any of the three cross-coupling reactions that
295 were investigated. This is possibly due to the relatively small
296 amount of glucose that was added to the reaction (cf. Scheme
297 12). EF-TEM analysis of the *in situ* formed nanoparticles
298 confirmed that the palladium was surrounded by a hydrophilic,
299 hydroxylated shell. The nature of this shell allowed for the facile
300 partitioning of the catalyst between the aqueous and organic
301 phases, which enabled catalyst recycling for up to four cycles
302 without significant loss of activity.

303 CONCLUSION

304 The importance of the addition of monosaccharides to metal-
305 catalyzed processes in organic chemistry has expanded rapidly
306 in recent years. These biorenewable materials can be used for a
307 number of important processes including as ligands for a metal
308 catalyst, to provide the appropriate reduction potential for a
309 chemical process, and as a reducing agent for the formation and
310 stabilization of catalytically active metal nanoparticles. These
311 recent developments in the field will provide the basis for
312 further rapid advancements. Looking forward, catalytic
313 processes in which the reducing potential of renewable sugars
314 is harnessed for the generation, stabilization and turnover of
315 catalytically active metal nanoparticles, sugar-powered catalysis,
316 will be developed. These processes have the potential to make
317 existing protocols greener in terms of time, expense and cost to
318 the environment, as well as allowing for the development of
319 novel metal-catalyzed processes that are currently not possible.
320 Additionally, the inherent chirality of the monosaccharides will
321 be harnessed in order to develop catalytic access to
322 enantiomerically enriched products. In conclusion, the addition
323 of monosaccharides to metal-catalyzed processes has resulted in
324 a number of important new methods that allow access to the

small molecules on which we have all come to rely. It is
expected that innovative new applications will be developed
that build on this exciting research.

328 AUTHOR INFORMATION

Corresponding Authors

*S. H. Kyne. Email: skyne@lincoln.ac.uk. Tel: +44 (0)15 2283 7402.

*J. E. Camp. Email: j.e.Camp@hud.ac.uk. Tel: +44 (0)14 8447 3180.

Notes

The authors declare no competing financial interest.

Biographies



Sara H. Kyne obtained her Ph.D. from The University of Melbourne (Australia) under the supervision of Prof. Carl H. Schiesser in the area of physical–organic intramolecular radical chemistry. She then undertook a postdoctoral position with Prof. Jonathan M. Percy (University of Strathclyde, UK) and a Marie Curie Intra European Fellowship with Prof. Louis Fensterbank (Université Pierre et Marie Curie, France). She is currently a lecturer at the University of Lincoln working on the development of sustainable catalysis and radical methodology.



Jason E. Camp obtained his Ph.D. from The Pennsylvania State University under the supervision of Prof. Steven Weinreb working on the total synthesis of the chartellamide and chartelline family of marine natural products. He then was a postdoctoral fellow working with Prof. Donald Craig (Imperial College London) before obtaining lectureships at the University of Nottingham and Queen Mary University of London. He is currently a senior lecturer at the University of Huddersfield working on the development of novel autotandem catalysis methods as well as sugar-powered catalysis protocols.

355 ■ REFERENCES

- (1) Mattson, A. M.; Jensen, C. O. Colorimetric determination of reducing sugars with triphenyltetrazolium chloride. *Anal. Chem.* **1950**, *22*, 182–185.
- (2) Benedict, S. R. A reagent for the detection of reducing sugars. *J. Biol. Chem.* **1908**, *5*, 485–487.
- (3) Fehling, H. Die quantitative bestimmung von zucker und stärke mittelst kupfervitriol. *Justus Liebigs Ann. Chem.* **1849**, *72*, 106–113.
- (4) For a recent review, see: Molnár, Á.; Papp, A. The use of polysaccharides and derivatives in palladium-catalyzed coupling reactions. *Catal. Sci. Technol.* **2014**, *4*, 295–310.
- (5) For a recent review, see: Kaushik, M.; Moores, A. Review: nanocelluloses as versatile supports for metal nanoparticles and their applications in catalysis. *Green Chem.* **2016**, *18*, 622–637.
- (6) Rezayat, M.; Blundell, R. K.; Camp, J. E.; Walsh, D. A.; Thielemans, W. Green, one step synthesis of catalytically active palladium nanoparticles supported on cellulose nanocrystal. *ACS Sustainable Chem. Eng.* **2014**, *2*, 1241–1250.
- (7) Kaushik, M.; Basu, K.; Benoit, C.; Cirtiu, C. M.; Vali, H.; Moores, A. Cellulose nanocrystals as chiral inducers: Enantioselective catalysis and transmission electron microscopy 3D characterization. *J. Am. Chem. Soc.* **2015**, *137*, 6124–6127.
- (8) Yasukawa, T.; Miyamura, H.; Kobayashi, S. Cellulose-supported chiral rhodium nanoparticles as sustainable heterogeneous catalysts for asymmetric carbon-carbon bond-forming reaction. *Chem. Sci.* **2015**, *6*, 6224–6229.
- (9) Ghaderi, A.; Gholinejad, M.; Firouzabadi, H. Palladium deposited on naturally occurring supports as a powerful catalyst for carbon-carbon bond formation reactions. *Curr. Org. Chem.* **2016**, *20*, 327–348.
- (10) Leuckart, R. Ueber die einwirkung von phenylcyanat auf phenole und phenoläther. *Ber. Dtsch. Chem. Ges.* **1885**, *18*, 2341–2344.
- (11) Wallach, O. Zur kenntniss der terpene und der ätherischen oele. ueber die ueberführung von ketonen und aldehyden in basen. *Justus Liebigs Ann. Chem.* **1905**, *343*, 54–74.
- (12) Webers, V. J.; Bruce, W. F. The Leuckart reaction: A study of the mechanism. *J. Am. Chem. Soc.* **1948**, *70*, 1422–1424.
- (13) Gibson, H. W. Chemistry of formic acid and its simple derivatives. *Chem. Rev.* **1969**, *69*, 673–692.
- (14) Ledoux, A.; Sandjong Kuigwa, L.; Framery, E.; Andrioletti, B. A highly sustainable route to pyrrolidone derivatives – direct access to biosourced solvents. *Green Chem.* **2015**, *17*, 3251–3254.
- (15) Wei, Y.; Wang, C.; Jiang, X.; Xue, D.; Liu, Z.-T.; Xiao, J. Catalyst-free transformation of levulinic acid into pyrrolidinones with formic acid. *Green Chem.* **2014**, *16*, 1093–1096.
- (16) Neochoritis, C. G.; Stotani, S.; Mishra, B.; Dömling, A. Efficient isocyanide-less isocyanide-based multicomponent reactions. *Org. Lett.* **2015**, *17*, 2002–2005.
- (17) Plazl, I. P.; Leskovšek, S.; Koloini, T. Hydrolysis of sucrose by conventional and microwave heating in stirred tank reactor. *Chem. Eng. J.* **1995**, *59*, 253–257.
- (18) Breuer, M.; Ditrich, K.; Habicher, T.; Hauer, B.; Keßeler, M.; Stürmer, R.; Zelinski, T. Industrial methods for the production of optically active intermediates. *Angew. Chem., Int. Ed.* **2004**, *43*, 788–824.
- (19) For a recent example, see: Mensah, E.; Camasso, N.; Kaplan, W.; Nagorny, P. Chiral phosphoric acid directed regioselective acetalization of carbohydrate-derived 1,2-diols. *Angew. Chem., Int. Ed.* **2013**, *52*, 12932–12936.
- (20) For a recent example, see: Caratzoulas, S.; Davis, M. E.; Gorte, R. J.; Gounder, R.; Lobo, R. F.; Nikolakis, V.; Sandler, S. I.; Snyder, M. A.; Tsapatsis, M.; Vlachos, D. G. Challenges of and insights into acid-catalyzed transformations of sugars. *J. Phys. Chem. C* **2014**, *118*, 22815–22833.
- (21) For a recent example, see: Galbis, J. A.; de Garcia García-Martín, M.; de Paz, V.; Galbis, E. Synthetic polymers from sugar-based monomers. *Chem. Rev.* **2016**, *116*, 1600–1636.
- (22) For a recent example, see: Saloranta, T.; Leino, R. Unprotected carbohydrates as starting material in chemical synthesis: Not just a challenge but an opportunity. *Synlett* **2015**, *26*, 421–425.
- (23) For a recent example, see: Lourenço, L. M. O.; Neves, M. G. P. M. S.; Cavaleiro, J. A. S.; Tomé, J. P. C. Synthetic approaches to glycopthalocyanines. *Tetrahedron* **2014**, *70*, 2681–2698.
- (24) For a recent example, see: Adhikary, N. D.; Kwon, S.; Chung, W.-J.; Koo, S. One-pot conversion of carbohydrates into pyrrole-2-carbaldehydes as sustainable platform chemicals. *J. Org. Chem.* **2015**, *80*, 7693–7701.
- (25) Woodward, S.; Diéguez, M.; Pámies, O. Use of sugar-based ligands in selective catalysis: Recent developments. *Coord. Chem. Rev.* **2010**, *254*, 2007–2030.
- (26) Thakur, K. G.; Sekar, G. D-Glucose as green ligand for selective copper-catalyzed phenol synthesis from aryl halides with an easy catalyst removal. *Chem. Commun.* **2011**, *47*, 6692–6694.
- (27) Cheng, D.; Gan, F.; Qian, W.; Bao, W. D-Glucosamine – a natural ligand for the N-arylation of imidazoles with aryl and heteroaryl bromides catalyzed by CuI. *Green Chem.* **2008**, *10*, 171–173.
- (28) Thakur, K. G.; Ganapathy, D.; Sekar, G. D-Glucosamine as a green ligand for copper catalyzed synthesis of primary aryl amines from aryl halides and ammonia. *Chem. Commun.* **2011**, *47*, 5076–5078.
- (29) Thakur, K. G.; Srinivas, K. S.; Chiranjeevi, K.; Sekar, G. D-Glucosamine as an efficient ligand for the copper-catalyzed selective synthesis of anilines from aryl halides and NaN₃. *Green Chem.* **2011**, *13*, 2326–2329.
- (30) Wen, M.; Shen, C.; Wang, L.; Zhang, P.; Jin, J. An efficient D-glucosamine-based copper catalyst for C–X couplings and its application in the synthesis of nilotinib intermediate. *RSC Adv.* **2015**, *5*, 1522–1528.
- (31) Yang, M.; Shen, S.; Li, Y.; Shen, C.; Zhang, P. D-Glucosamine as a green ligand for copper catalyzed synthesis of aryl sulfones from aryl halides and sodium sulfonates. *RSC Adv.* **2014**, *4*, 26295–26300.
- (32) Sova, M.; Frlan, R.; Gobec, S.; Stavber, G.; Časar, Z. D-Glucosamine in iron-catalysed cross-coupling reactions of Grignards with allylic and vinylic bromides: application to the synthesis of a key sitagliptin precursor. *Appl. Organomet. Chem.* **2015**, *29*, 528–535.
- (33) Amini, M.; Etemadi, H. D-Glucosamine as an efficient and green additive for palladium-catalyzed Heck reaction. *Chem. Pap.* **2013**, *67*, 759–763.
- (34) For a comprehensive review, see: Dahl, J. A.; Maddux, B. L. S.; Hutchison, J. E. Toward greener nanosynthesis. *Chem. Rev.* **2007**, *107*, 2228–2269.
- (35) For a recent review, see: Varma, R. S. Journey on greener pathways: from the use of alternate energy inputs and benign reaction media to sustainable applications of nano-catalysts in synthesis and environmental remediation. *Green Chem.* **2014**, *16*, 2027–2041.
- (36) For a recent review, see: Gawande, M. B.; Shelke, S. N.; Zboril, R.; Varma, R. S. Microwave-assisted chemistry: synthetic applications for rapid assembly of nanomaterials and organics. *Acc. Chem. Res.* **2014**, *47*, 1338–1348.
- (37) For a recent review, see: Virkutyte, J.; Varma, R. S. Green synthesis of metal nanoparticles: Biodegradable polymers and enzymes in stabilization and surface functionalization. *Chem. Sci.* **2011**, *2*, 837–846.
- (38) For a recent review, see: Narayanan, R. Synthesis of green nanocatalysts and industrially important green reactions. *Green Chem. Lett. Rev.* **2012**, *5*, 707–725.
- (39) For a recent example, see: Shervani, Z.; Yamamoto, Y. Carbohydrate-directed synthesis of silver and gold nanoparticles: Effect of the structure of carbohydrates and reducing agents on the size and morphology of the composites. *Carbohydr. Res.* **2011**, *346*, 651–658.
- (40) For a recent example, see: Shervani, Z.; Yamamoto, Y. Size and morphology controlled synthesis of gold nanoparticles in green solvent: Effect of reducing agents. *Mater. Lett.* **2011**, *65*, 92–95.

- (41) For a recent example, see: Moukarzel, W.; Fitremann, J.; Marty, J.-D. Seed-less amino-sugar mediated synthesis of gold nanostars. *Nanoscale* **2011**, *3*, 3285–3290.
- (42) For a recent example, see: Fellingner, T.-P.; White, R. J.; Titirici, M.-M.; Antonietti, M. Borax-mediated formation of carbon aerogels from glucose. *Adv. Funct. Mater.* **2012**, *22*, 3254–3260.
- (43) For a recent example, see: Kahrilas, G. A.; Haggren, W.; Read, R. L.; Wally, L. M.; Fredrick, S. J.; Hiskey, M.; Prieto, A. L.; Owens, J. E. Investigation of antibacterial activity by silver nanoparticles prepared by microwave-assisted green syntheses with soluble starch, dextrose, and arabinose. *ACS Sustainable Chem. Eng.* **2014**, *2*, 590–598.
- (44) Gole, A.; Kumar, A.; Phadtare, S.; Mandale, A. B.; Sastry, M. Glucose induced *in-situ* reduction of chloroaurate ions entrapped in a fatty amine film: formation of gold nanoparticle–lipid composites. *PhysChemComm* **2001**, *4*, 92–95.
- (45) Xiong, L.; Tong, Z.-H.; Li, L.-L.; Yu, H.-Q. Morphology dependent antimicrobial activity of Cu/Cu₂O nanoparticles. *Ecotox-icology* **2015**, *24*, 2067–2072.
- (46) Jin, M.; He, G.; Zhang, H.; Zeng, J.; Xie, Z.; Xia, Y. *Angew. Chem., Int. Ed.* **2011**, *50*, 10560–10564.
- (47) Huang, X.; Li, Y.; Zhou, H.; Zhong, X.; Duan, X.; Huang, Y. Simplifying the creation of dumbbell-like Cu-Ag nanostructures and their enhanced catalytic activity. *Chem. - Eur. J.* **2012**, *18*, 9505–9510.
- (48) Stojanovic, Z.; Otoničar, M.; Lee, J.; Stevanovic, M. M.; Hwang, M. P.; Lee, K. H.; Choi, J.; Uskokovic, D. The solvothermal synthesis of magnetic iron oxide nanocrystals and the preparation of hybrid poly(l-lactide)–polyethyleneimine magnetic particles. *Colloids Surf., B* **2013**, *109*, 236–243.
- (49) Kumar, D. V. R.; Kim, I.; Zhong, Z.; Kim, K.; Lee, D.; Moon, J. Cu(II)–alkyl amine complex mediated hydrothermal synthesis of Cu nanowires: exploring the dual role of alkylamines. *Phys. Chem. Chem. Phys.* **2014**, *16*, 22107–22115.
- (50) Sun, X.; Li, Y. Colloidal carbon spheres and their core/shell structures with noble-metal nanoparticles. *Angew. Chem., Int. Ed.* **2004**, *43*, 597–601.
- (51) Chen, C.; Sun, X.; Jiang, X.; Niu, D.; Yu, A.; Liu, Z.; Li, J. G. A two-step hydrothermal synthesis approach to monodispersed colloidal carbon spheres. *Nanoscale Res. Lett.* **2009**, *4*, 971–976.
- (52) Kong, L.; Lu, X.; Bian, X.; Zhang, W.; Wang, C. Accurately tuning the dispersity and size of palladium particles on carbon spheres and using carbon spheres/palladium composite as support for polyaniline in H₂O₂ electrochemical sensing. *Langmuir* **2010**, *26*, 5985–5990.
- (53) For a recent example, see: Zhang, P.; Gong, Y.; Li, H.; Chen, Z.; Wang, Y. Solvent-free aerobic oxidation of hydrocarbons and alcohols with Pd@N-doped carbon from glucose. *Nat. Commun.* **2013**, *4*, 1593–1604.
- (54) Nie, T.; Wu, H.; Wong, K.-H.; Chen, T. Facile synthesis of highly uniform selenium nanoparticles using glucose as the reductant and surface decorator to induce cancer cell apoptosis. *J. Mater. Chem. B* **2016**, *4*, 2351–2358.
- (55) Chen, C.; Sun, X.; Jiang, X.; Niu, D.; Yu, A.; Liu, Z.; Li, J. G. A two-step hydrothermal synthesis approach to monodispersed colloidal carbon spheres. *Nanoscale Res. Lett.* **2009**, *4*, 971–976.
- (56) Noh, E. S. A.; Roy, M.; Sarkar, S. Glucose stabilized magnetic palladium nanoparticles exhibiting enhanced magnetic properties under exposure to hydrogen. *Mater. Express* **2012**, *2*, 275–284.
- (57) Sun, X.; Li, Y. Colloidal carbon spheres and their core/shell structures with noble-metal nanoparticles. *Angew. Chem., Int. Ed.* **2004**, *43*, 597–601.
- (58) Kong, L.; Lu, X.; Bian, X.; Zhang, W.; Wang, C. Accurately tuning the dispersity and size of palladium particles on carbon spheres and using carbon spheres/palladium composite as support for polyaniline in H₂O₂ electrochemical sensing. *Langmuir* **2010**, *26*, 5985–5990.
- (59) Pal, R.; Chatterjee, N.; Roy, M.; Noh, E. S. A.; Sarkar, S.; Jaisankar, P.; Sarkar, S.; Sen, A. K. *Tetrahedron Lett.* **2016**, *57*, 43–47.
- (60) Rostamizadeh, S.; Aryan, R.; Ghaieni, H. R. Aqueous 1 M glucose solution as a novel and fully green reaction medium and catalyst for the oxidant-free synthesis of 2-arylbenzimidazoles. *Synth. Commun.* **2011**, *41*, 1794–1804.
- (61) Aryan, R.; Beyzaei, H.; Sadeghi, F. Facile synthesis of some novel tetrasubstituted 2,4-diaminopyrimidine derivatives in aqueous glucose solution as a fully green medium and promoter. *J. Heterocyclic Chem.* **2015**, DOI: 10.1002/jhet.2514.
- (62) Weidlich, T.; Opršal, J.; Krejčová, A.; Jašúrek, B. Effect of glucose on lowering Al–Ni alloy consumption in dehalogenation of halogenoanilines. *Monatsh. Chem.* **2015**, *146*, 613–620.
- (63) Kumar, M.; Sharma, U.; Sharma, S.; Kumar, V.; Singh, B.; Kumar, N. Catalyst-free water mediated reduction of nitroarenes using glucose as a hydrogen source. *RSC Adv.* **2013**, *3*, 4894–4898.
- (64) For related nitroarene to aniline reductions using reducing sugars, see: Rajapakse, A.; Barnes, C. L.; Gates, K. S. Synthesis and crystal structure of the azoxydichinyl helicene, pyrido[3,2-*f*]quinolino-[6,5-*c*]cinnoline 5-oxide monohydrate. *J. Chem. Crystallogr.* **2011**, *41*, 1712–1716.
- (65) For a related nitroarene to aniline reduction using reducing sugars, see: Soloniewicz, R.; Teodorczyk, M. Spectrophotometric determination of reducing sugars with aromatic nitro compounds. *Microchim. Acta* **1982**, *77*, 105–114.
- (66) For a related nitroarene to aniline reduction using reducing sugars, see: Galbraith, H. W.; Degering, E. F.; Hitch, E. F. The alkaline reduction of aromatic nitro compounds with glucose. *J. Am. Chem. Soc.* **1951**, *73*, 1323–1324.
- (67) García, M. A.; Ríos, Z. G.; González, J.; Pérez, V. M.; Lara, N.; Fuentes, A.; González, C.; Corona, D. Cuevas-Yañez, E. The use of glucose as alternative reducing agent in copper-catalyzed alkyne-azide cycloaddition. *Lett. Org. Chem.* **2011**, *8*, 701–706.
- (68) Kumar, Y.; Bahadur, V.; Singh, A. K.; Parmar, V. S.; Singh, B. K. Microwave-assisted copper azide alkyne cycloaddition (CuAAC) reaction using D-glucose as a better alternative reductant. *J. Indian Chem. Soc.* **2013**, *90*, 1893–1903.
- (69) Kumar, Y.; Bahadur, V.; Singh, A. K.; Parmar, V. S.; Van der Eycken, E.; Singh, B. K. Microwave-assisted Cu(I)-catalyzed, three-component synthesis of 2-(4-((1-phenyl-1H-1,2,3-triazol-4-yl)-methoxy)phenyl)-1H-benzo[d]imidazoles. *Beilstein J. Org. Chem.* **2014**, *10*, 1413–1420.
- (70) Kumar, Y.; Matta, A.; Kumar, P.; Parmar, V. S.; Van der Eycken, E.; Singh, B. K. Cu(I)-catalyzed microwave-assisted synthesis of 1,2,3-triazole linked with 4-thiazolidinones: a one-pot sequential approach. *RSC Adv.* **2015**, *5*, 1628–1639.
- (71) Zhang, Y.; Liu, Y.; Wan, J.-P. Copper-catalyzed three-component reactions of phenols, acyl chlorides and Wittig reagents for the synthesis of β -aryloxy acrylates. *New J. Chem.* **2015**, *39*, 1567–1569.
- (72) Guchhait, S. K.; Chandgude, A. L.; Priyadarshani, I. J. *Org. Chem.* **2012**, *77*, 4438–4444.
- (73) Balijapalli, U.; Iyer, S. K. CuO–CuAl₂O₄ and D-glucose catalyzed synthesis of a family of excited state intramolecular proton transfer imidazo[1,2-*a*]pyridine analogues and their optical properties. *Dyes Pigm.* **2015**, *121*, 88–98.
- (74) Shen, C.; Shen, H.; Yang, M.; Xia, C.; Zhang, P. A novel D-glucosamine-derived pyridyl-triazole@palladium catalyst for solvent-free Mizoroki–Heck reactions and its application in the synthesis of Axitinib. *Green Chem.* **2015**, *17*, 225–230.
- (75) Vaccaro, L.; Petrucci, C.; Strappaveccia, G.; Giacalone, F.; Gruttadauria, M.; Pizzo, F. An E-Factor Minimized Protocol for a Sustainable and Efficient Heck Reaction in Flow. *ACS Sustainable Chem. Eng.* **2014**, *2*, 2813–2819.
- (76) Khalafi-Nezhad, A.; Panahi, F. Size-controlled synthesis of palladium nanoparticles on a silica–cyclodextrin substrate: A novel palladium catalyst system for the heck reaction in water. *ACS Sustainable Chem. Eng.* **2014**, *2*, 1177–1186.
- (77) Gatard, S.; Salmon, L.; Deraedt, C.; Ruiz, J.; Astruc, D.; Bouquillon, S. Palladium nanoparticles stabilized by glycodendrimers

- and their application in catalysis. *Eur. J. Inorg. Chem.* **2014**, 2014, 4369–4375.
- (78) Puthiaraj, P.; Ahn, W.-S. Highly active palladium nanoparticles immobilized on NH₂-MIL-125 as efficient and recyclable catalysts for Suzuki–Miyaura cross coupling reaction. *Catal. Commun.* **2015**, 65, 91–95.
- (79) Song, H.-Q.; Zhu, Q.; Zheng, X.-J.; Chen, X.-G. J. One-step synthesis of three-dimensional graphene/multiwalled carbon nanotubes/Pd composite hydrogels: an efficient recyclable catalyst for Suzuki coupling reactions. *J. Mater. Chem. A* **2015**, 3, 10368–10377.
- (80) Hardy, J. J. E.; Hubert, S.; Macquarrie, D. J.; Wilson, A. J. Chitosan-based heterogeneous catalysts for Suzuki and Heck reactions. *Green Chem.* **2004**, 6, 53–56.
- (81) Putta, C. B.; Ghosh, S. Palladium nanoparticles on amphiphilic carbon spheres: A green catalyst for Suzuki–Miyaura reaction. *Adv. Synth. Catal.* **2011**, 353, 1889–1896.
- (82) Monopoli, A.; Calò, V.; Ciminale, F.; Cotugno, P.; Angelici, C.; Cioffi, N.; Nacci, A. Glucose as a clean and renewable reductant in the Pd-nanoparticle-catalyzed reductive homocoupling of bromo- and chloroarenes in water. *J. Org. Chem.* **2010**, 75, 3908–3911.
- (83) Monopoli, A.; Cotugno, P.; Palazzo, G.; Ditaranto, N.; Mariano, B.; Cioffi, N.; Ciminale, F.; Nacci, A. Ullmann Homocoupling catalysed by gold nanoparticles in water and ionic liquid. *Adv. Synth. Catal.* **2012**, 354, 2777–2788.
- (84) Camp, J. E.; Dunsford, J. J.; Cannons, E. P.; Restorick, W. J.; Gadzhieva, A.; Fay, M. W.; Smith, R. J. Glucose-derived palladium(0) nanoparticles as *in situ*-formed catalysts for Suzuki–Miyaura cross-coupling reactions in isopropanol. *ACS Sustainable Chem. Eng.* **2014**, 2, 500–505.
- (85) Xu, S.-Y.; Ruan, Y.-B.; Luo, X.-X.; Gao, Y.-F.; Zhao, J.-S.; Shen, J.-S.; Jiang, Y.-B. Enhanced saccharide sensing based on simple phenylboronic acid receptor by coupling to Suzuki homocoupling reaction. *Chem. Commun.* **2010**, 46, 5864–5866.
- (86) Xu, S.-Y.; Wang, H.-C.; Flower, S. E.; Fossey, J. S.; Jiang, Y.-B.; James, T. D. Suzuki homo-coupling reaction based fluorescent sensors for monosaccharides. *RSC Adv.* **2014**, 4, 35238–35241.
- (87) For a recent review, see: Camp, J. E. Auto-Tandem Catalysis: Activation of multiple, mechanistically distinct process by a single catalyst. *Eur. J. Org. Chem.* **2016**, DOI: 10.1002/ejoc.201600803.
- (88) For a recent example, see: Lester, R. P.; Dunsford, J. J.; Camp, J. E. A Multifaceted Catalysis Approach to Nitrile Activation: Direct synthesis of halogenated allyl amides from allylic alcohols. *Org. Biomol. Chem.* **2013**, 11, 7472–7476.
- (89) Rohilla, S.; Pant, P.; Jain, N. Pd/mannose promoted tandem cross coupling-nitro reduction: expedient synthesis of aminobiphenyls and aminostilbenes. *RSC Adv.* **2015**, 5, 31311–31317.
- (90) Camp, J. E.; Dunsford, J. J.; Dacosta, O. S. G.; Blundell, R. K.; Adams, J.; Britton, J.; Smith, R. J.; Bousfield, T. W.; Fay, M. W. Recyclable glucose-derived palladium(0) nanoparticles as *in situ*-formed catalysts for cross-coupling reactions in aqueous media. *RSC Adv.* **2016**, 6, 16115–16121.